



Coupling of high-quality-factor optical resonators

Patrice Salzenstein, Michel Mortier, Hélène Sérrier-Brault, Rémi Henriët,
Aurélien Coillet, Yanne Kouomou Chembo, Alphonse Rasoloniaina, Yannick
Dumeige, Patrice Féron

► To cite this version:

Patrice Salzenstein, Michel Mortier, Hélène Sérrier-Brault, Rémi Henriët, Aurélien Coillet, et al.. Coupling of high-quality-factor optical resonators. *Physica Scripta*, 2013, T157, pp.014024. 10.1088/0031-8949/2013/T157/014024 . hal-00909283

HAL Id: hal-00909283

<https://hal.science/hal-00909283>

Submitted on 26 Nov 2013

HAL is a multi-disciplinary open access archive for the deposit and dissemination of scientific research documents, whether they are published or not. The documents may come from teaching and research institutions in France or abroad, or from public or private research centers.

L'archive ouverte pluridisciplinaire **HAL**, est destinée au dépôt et à la diffusion de documents scientifiques de niveau recherche, publiés ou non, émanant des établissements d'enseignement et de recherche français ou étrangers, des laboratoires publics ou privés.

Coupling of high quality factor optical resonators

Patrice Salzenstein^a, Michel Mortier^b, Hélène Sérrier-Brault^b, Rémi Henriet^a, Aurélien Coillet^a, Yanne K. Chembo^a, Alphonse Rasoloniaina^c, Yannick Dumeige^c, Patrice Féron^c

^a Centre National de la Recherche Scientifique (CNRS), Franche Comté Electronique Thermique Optique Sciences et Technologies (FEMTO-ST), 32 avenue de l'Observatoire, F25044 Besançon cedex, FRANCE

^b Centre National de la Recherche Scientifique (CNRS), LCMCP, Chimie ParisTech, 11, rue Pierre et Marie Curie, 75231 PARIS Cedex 05 FRANCE

^c Enssat-Foton, 6, rue de Kerampont BP 80518 22305 Lannion cedex FRANCE

E-mail: patrice.salzenstein@femto-st.fr

Abstract. We improve theoretically and experimentally the problem of the coupling between a high Q-factor resonator and its external coupler. We have observed oscillations of ringing induced by the sweeping of the excitation frequency of an active micro sphere. Thanks to this approach, quality factor of an optical resonator was measured and we obtained $Q = 5.8 \times 10^8$.

1. Introduction.

Optical resonators with high quality factor (Q-factor) present a great interest for several applications in optoelectronic [1], metrology or fundamental physics [2, 3]. For instance they can be used in optical filtering, all optical switching, low threshold non-linear optics, etc. Main results have been obtained since 1996 [4]. Recently results have been obtained with mono-crystalline such as MgF_2 , Quartz or CaF_2 whispering gallery mode (WGM) resonators [5-9]. Rare earth element doped micro spheres are tiny lasers which intrinsically offer narrow line width emission [10]. A key feature of the characterization of the resonators is to perform a good coupling. Performing this characterization is quite challenging because it is a necessary but difficult technique. That's why we improve theoretically and experimentally the problem of the coupling between a high Q-factor resonator and its external coupler. They are characterized by different methods such as slow and fast frequency sweeping [11]. Resonators can be coupled to tapered fibres or prisms. We focus here on characterizations techniques of passive optical resonators or active (Erbium doped ZBLALiP [12, 13]) WGM resonators in terms of Q-factor determination.

2. Properties of a doped micro resonator.

Figure 1 shows schematically the WGM micro resonator and its access line. It is possible to isolate each resonance, although the resonator is inherently multi mode. We can work with each resonance separately. The studied resonator is then considered single mode.

A mode with an amplitude $a(t)$ is characterized by the time life of the field τ_0 limited by losses, by the coupling rate of the access line which is proportional to $1/\tau_e$ and by the angular frequency of the resonance ω_0 . The amplitude of the input signal is noted $s_{in}(t)$, we can then calculate the amplitude of

the output signal $s_{out}(t) = -s_{in}(t) + \sqrt{\frac{2}{\tau_e}} a(t)$ by integration :

$$\frac{da}{dt} = \left(j\omega_0 - \frac{1}{\tau} \right) a(t) + \sqrt{\frac{2}{\tau_e}} s_{in}(t) \quad (1)$$

In equation (1), $\tau = (1/\tau_0 + 1/\tau_e)^{-1}$ is the time life of the field in the cavity related to factor $Q = \omega_0 \tau / 2$. We assume that input signal is harmonic $s_{in}(t) = S_{in} e^{j\omega t}$ and output signal is $s_{out}(t) = S_{out} e^{j\omega t}$. As a consequence, the transfer function is given by :

$$T(\delta) = \frac{S_{out}}{S_{in}} = \frac{\left(\frac{1}{\tau_e} - \frac{1}{\tau_0} \right)^2 + 4\pi^2 \delta^2}{\left(\frac{1}{\tau_e} + \frac{1}{\tau_0} \right)^2 + 4\pi^2 \delta^2} \quad (2)$$

In this expression δ is the frequency mismatch given by $\omega = \omega_0 + 2\pi\delta$. Different configurations are possible according to the relative value of τ_e and τ_0 . If $\tau_0 \rightarrow \infty$ then resonator has no losses, so $T(\delta) = 1$ as illustrated on figure 1(b). But if we suppose that $\tau_e = \tau_0$, then the resonator is in critical coupling and transmission at the resonance $T(0)$ becomes zero. And if $\tau_0 < -\tau_e$, resonator presents some gain (even if it stays less than the LASER threshold) and it behaves like an amplifier, then $T(0) > 1$ [14].

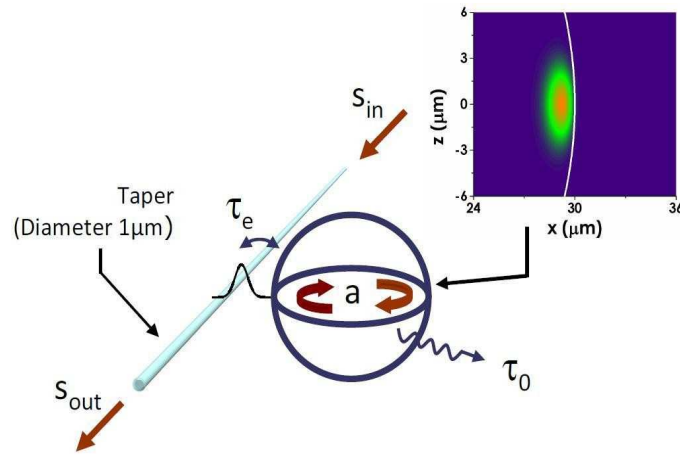


Figure 1. Scheme of the micro resonator and its access line.

3. Measurements.

Amplification measurements were performed in Erbium doped ZBLALiP micro spheres. Diameters of the micro spheres are between 50 μm and 150 μm . These spheres are obtained by fusion in a microwave inductively coupled plasma [10]. Usual measurement method consists in sweeping the frequency of a Laser emitting around 1550 nm, in order to obtain a description of one resonance for the micro sphere. Simultaneously, this micro sphere is pumped by a laser at 1480 nm emitting in opposition of propagation as described in Figure 2.

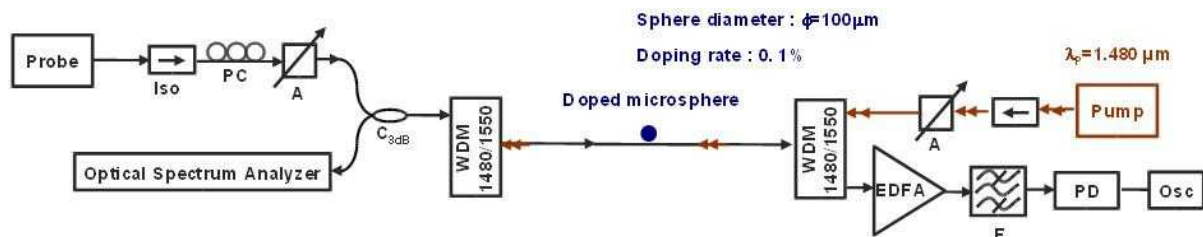


Figure 2. Setup for measuring the selective gain. Probe : extended cavity laser diode with a 150 kHz spectral width, emitting around 1550 nm. OSA : Optical Spectrum Analyzer, CP: polarization controller, MUX : multiplexer 1550/1480, PWM : power meter, EDFA : optical amplifier, F : tunable filter with a 50 pm spectral width. 'pump' is a Laser diode emitting around 1480nm. The diameter of the micro sphere is 105 μm .

Thanks to the pumping, the sphere delivers a Laser signal for one or several resonances far enough from the studying resonance: it helps to stabilize the gain. Optical Spectrum analyzer (OSA) helps for the control the micro sphere Laser emission. To illustrate how this technology can be applied, laser frequency is swept slowly enough to stay in stationary approximation, to describe thin resonance as illustrated in Figure 3.

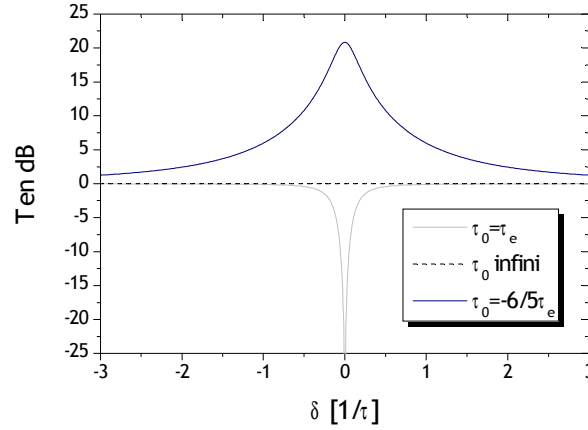


Figure 3. Theoretical spectra obtained for $3 \tau_0$.

Our approach is different. The analysis begins by sweeping very quickly the frequency of the Laser. This process is analogous to what occurs when the speed is slow, but provides definitely an easier and unquestionably a precise determination of the Q-factor. This approach is implemented by utilizing the following process. This allows to work in the ringing regime of the micro sphere. It has already been demonstrated that it is possible to determine characteristic parameters of the micro sphere [11, 15] if we compare the profile of the ringing oscillations to an analytical model obtained thanks to Eq.(1) and to an incident field like $s_{in}(t) = S_{in} e^{j(\omega_i + \pi V_S t)t}$. The sweeping speed of the Laser V_S , is often difficult to obtain precisely. But it is directly obtained by the method describes above. The results are illustrated in Figure 4, where two time profiles are obtained on the same resonance, with two different speeds (the second one is two time more quickly) for sweeping the Laser. While the deduced speeds are in the good ratio, adjustment provides almost the same results for τ_0 and τ_e . Observed differences for τ_0 and τ_e are mainly due to the fluctuations of the taper position. It has an influence on the signal coupling, and also on the pump. When performing the adjustment from the obtained ringing oscillation profiles, it has to be underlined that we deduce a quality factor as high as $Q = 5.8 \times 10^8$. The analysis proceeds by matching the theoretical and experimental curves. Q-factor estimation may be quickly obtained, and the efficiency of such a fast sweeping is really good. This is the desired result, which gives great insight into the resonator coupling and Q-factor estimation problem.

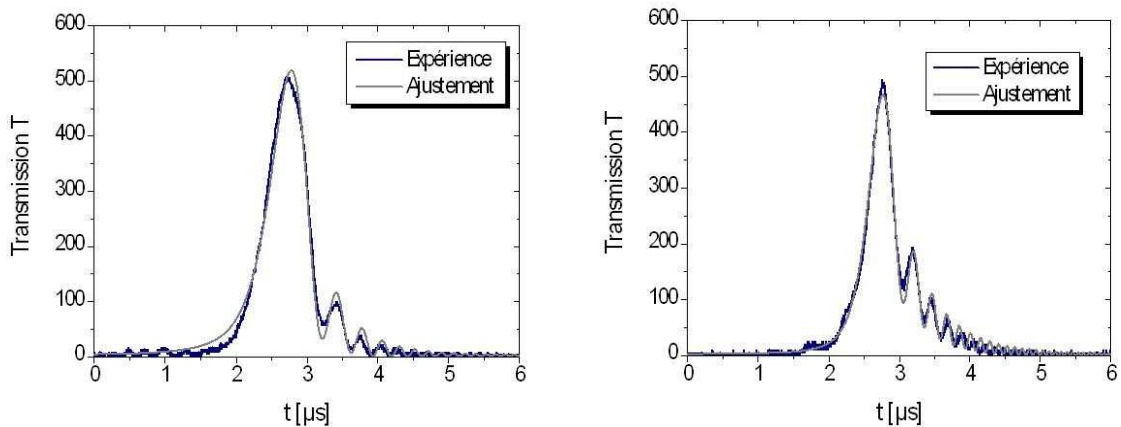


Figure 4. Obtained ringing oscillation profiles for two frequencies F driving the sweeping of the tunable Laser, $PS = 125$ nW, $PP = 7$ mW. (a) – left: $F = 400$ Hz, these values are deduced from the adjustment : $\tau_0 = -40.9$ ns, $\tau_e = 38.8$ ns, $V_S = 2.2$ MHz/ μ s, $Q = 4.4 \times 10^8$ and $T(0) = 31.2$ dB. (b) –

right: $F = 800$ Hz, also deduced from the adjustment : $\tau_0 = -39.2$ ns, $\tau_e = 37.6$ ns, $V/S = 4.1$ MHz/ μ s,
 $Q = 5.8 \times 10^8$ et $T(0) = 33.9$ dB.

4. Coupling with passive resonator and integration into an oscillator .

An optoelectronic oscillator (OEO) with an optical resonator coupled to an optical fiber, delivers a free spectral range microwave signal [1]. To implement this OEO in terms of miniaturization, it is possible to use a high WGM resonator with magnesium fluoride or calcium fluoride for microwave photonics applications. We have fabricated and characterized 5 mm diameter toroid MgF_2 and 12 mm CaF_2 resonators with a good surface roughness (1 nm). Quality factor better than 3.4×10^8 for magnesium fluoride [7] and 1.4×10^8 for calcium fluoride were measured by cavity ring-down measurements. Even if an optical line can be used as a frequency selective component in the OEO loop, the use of the mini-resonator leads to a significant reduction of the oscillator size. Further work consists in measuring the phase noise on dedicated instruments developed at the laboratory [16, 17]. We can also reduce or eliminate sensitivity to vibration by using a refractive index adapter gel. Q factor of resonators can still be improved by a better polishing of the crystal coupled to other treatments.

5. Conclusion.

The work performed here is significant in the sense that it appears that the problem of the coupling between a high Q-factor resonator and its external coupler has been theoretically and experimentally improved. The key is to recognize that oscillations of ringing induced by the sweeping of the excitation frequency of an active micro sphere are observed. Measured apparent gain is approximatively 27dB (up to 33.9 dB in stationary regime) in a 330 kHz band corresponding in the best case to a high quality factor $Q = 5.8 \times 10^8$. All of these approaches have been developed to address high quality factor resonator characterization. Addressing the combination of resonator polishing with other treatment, such as thermal annealing, to improve the surface roughness, is still an active area of research to achieve higher Q factors.

Acknowledgements.

Authors acknowledge the French National Research Agency (ANR) grant "ANR 2010 BLAN 0312".

References.

- [1] K. Volyanskiy, P. Salzenstein, H. Tavernier, M. Pogurmirskiy, Y. K. Chembo, L. Larger, Optics Express, 18 (2010) 22358-22363.
- [2] K. J. Vahala, Nature (London), 424, (2003) 839.
- [3] V. Ilchenko and A. Matsko, IEEE J.Sel.Top.Quantum Electron., 12, (2006) 15–32.
- [4] X.S.Yao, L. Maleki, Optics Letters, 21 (1996) 483-485.
- [5] V.S. Ilchenko, A.A. Savchenkov, J. Byrd, I. Solomatine, A.B. Matsko, D. Seidel, L. Maleki, Optics Letters, 33(14) (2008) 1569-1571.
- [6] I.S. Grudin, N. Yu, L. Maleki, Optics Letters, 34 (2009) 878-880.
- [7] H. Tavernier, P. Salzenstein, K. Volyanskiy, Y. K. Chembo, L. Larger, IEEE Photonics Tech. Lett., 22 (2010) 1629-1631.
- [8] D.K. Armani, T.J. Kippenberg, S.M. Spillane and K.J. Vahala, Nature 421 (2003) 925.
- [9] P. Del'Haye, A. Schli  er, O. Arcizet, T. Wilken, R. Holzwarth, and T.J. Kippenberg, Nature 450 (2007) 1214-1217.
- [10] F. Lissillour, D. Messenger, G. St  phan, P. F  ron, Opt. Lett. 26 (2001) 1051-1053.
- [11] Y. Dumeige, S. Trebaol, L. Ghisa, Thi Kim Ngan Nguyen, H. Tavernier, P. F  ron, J. Opt. Soc. Am. B, 25(12) (2008) 2073-2080.
- [12] M. Mortier, P. Goldner, P. F  ron, G. M. St  phan, H. Xu, Z. P. Cai, J. Non-Cryst. Sol. 326 & 327 (2003) 505-509.
- [13] Z. P. Cai, H. Y Xu, G. St  phan, P. F  ron, M. Mortier, Opt. Comm 229 (2004) 311-315.
- [14] L. He, S. Ozdemir, Y.-F. Xiao, and L. Yang, IEEE J. Quantum Electron., 46, (2010) 1626–1633.
- [15] S. Trebaol, Y. Dumeige, and P. F  ron, Phys. Rev. A, 81, (2010) 043828.
- [16] Salzenstein P., Cussey J., Jouvenceau X., Tavernier H., Larger L., Rubiola E. and Sauvage G., Acta Physica Polonica A, 112(5), (2007) 1107-1111.
- [17] Salzenstein P., Pavlyuchenko E., Hmima A., Cholley N., Zarubin M., Galliou S., Chembo Y. K. and Larger L., Physica Scripta , T149, (2012) 014025.